

A Review on Microstructural and Mechanical Characteristics of Stir Cast Aluminium Hybrid Metal Matrix Composites (AHMMCs)

Vishnu Vardhana Naidu^{1*}, Dr. K. C. Varaprasad², Prof. K. Prahalada Rao³ and Prakash⁴
^{1,2} Department of Mechanical Engineering, Sree Vidyanikethan Engineering College, Tirupati, India.

³JNTUA college of Engineering, Ananthapuramu, India.

⁴ Metallurgical and Materials Engineering, National Institute of Technology, Warangal

E-mail:* vishnu234@gmail.com, drkcvaraprasad@gmail.com, drkprao1@yahoo.com, prakasharg@gmail.com

Abstract—Aluminium Hybrid Metal Matrix Composites (AHMMCs) have evoked a keen interest in recent times for potential applications in aerospace and automotive industries owing to their superior strength to weight ratio and high temperature resistance. In the past few years the global need for low cost, high performance and good quality materials has caused a shift in research from monolithic to composite materials. Reinforcements like particulate alumina, silicon carbide, graphite, fly ash, rice husk ash (RHA) etc can easily be incorporated in the melt using cheap and widely available stir casting method. The present review deals with the characterization of aluminium based hybrid composites developed by stir casting for advanced applications. The potential of a wide range of secondary reinforcements has been explored for the development of Aluminium Hybrid Metal Matrix Composites (AHMMCs) and the application area of these composites has been proposed. The focus is on the optimization of parameters for various properties of composites. Further, the influence of reinforcement's type and contents on the material properties has also been reviewed and discussed.

Index Terms— Aluminium Hybrid Metal Matrix Composites (AHMMCs), stir casting.

I. INTRODUCTION

The different reinforcing materials used in the development of AHMMCs can be classified into three broad groups, which are synthetic ceramic particulates, industrial wastes and agro waste derivatives. The final properties of the hybrid reinforcement depend on individual properties of the reinforcement selected and the matrix alloy [1-4]. Moreover, the processing route adopted for synthesizing AHMMCs depends on the nature of the matrix alloy and reinforcing materials which also influence the final properties of AHMMCs. This is because most of the parameters put into consideration during the design of AHMMCs are linked with the reinforcing materials. A few of such parameters are reinforcement type, size, shape, modulus of elasticity, hardness, distribution in the matrix among others [1,5]. Based on the published articles studied, the discussion on the combinations of reinforcement used in the synthesis of AHMMCs is divided into three broad groups. These are AHMMCs with two synthetic ceramic materials; an agro waste derivative combined with synthetic ceramic materials; and industrial waste combined with synthetic reinforcement [6-8].

The present study deals with the characterization of aluminium based hybrid composites developed by stir casting for advanced applications. The potential of a wide range of secondary reinforcements [6, 9-12] has been explored for the development of AHMMCs and the application area of these composites has been proposed. The focus is on the optimization of parameters for various properties of composites. Further, the influence of reinforcement's type and contents on the material properties has also been reviewed and discussed.

II. Manufacturing And Characterization

Boopathi et al. [2] have studied the microstructures of aluminium alloy (Al 2024) reinforced with different compositions of fly ash, SiC and their mixtures. It has been observed that the particles were not uniformly distributed in single reinforced composites and segregation of particles was clearly visible. This was attributed to the gravity-regulated segregation of the particles in the melt. But, the micrographs of Al/SiC/flyash hybrid composites indicate uniform distribution of particles at various concentrations Figure. 1(a) and (b).

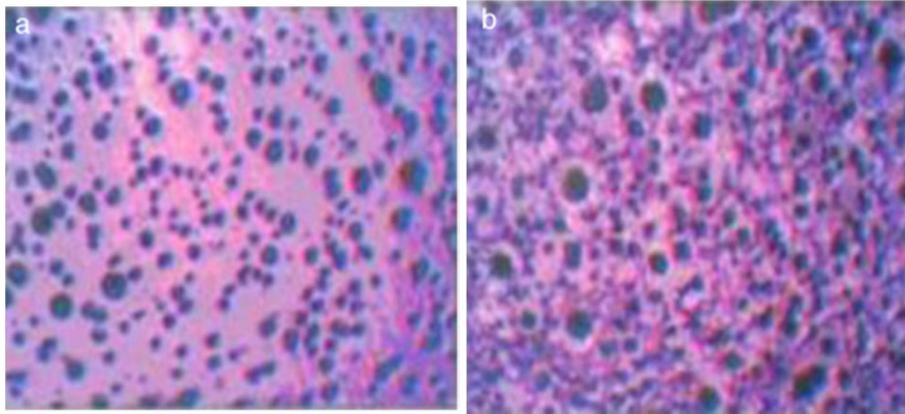


Figure 1. Optical micrograph of Al 2024/ (10% SiC + 10% fly ash) (a) before etching and (b) after etching (Boopathi et al. [2])

According to Rajmohan et al. [3], the hybrid reinforcements SiC and mica particles were uniformly distributed in Al356 alloy Figure 2(a). The aluminum, carbon, silicon and oxygen particles were clearly visible in the energy dispersive X-ray spectroscopy (EDS) profile Figure. 2(b). The scanning electron micrograph (SEM) images of composites are the evidence of successful incorporation of hybrid reinforcements in the Al-matrix. The clustering of SiC particles in matrix was attributed to their lower thermal conductivity and heat diffusivity than the alloy melt. The hotter SiC particles heat up the surrounding melt and delay the solidification process. Generally, the SiC particles are accumulated in the interdendritic regions and geometrical trapping by dendrites is not observed in the micrographs. This suggests that SiC particles are always pushed by dendrite fronts during solidification process.

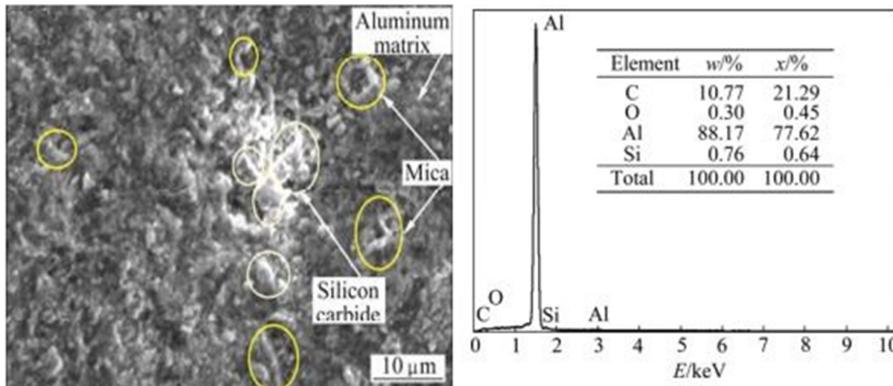


Figure 2. (a) SEM image of Al/10SiC-3mica composite (b) EDS spectrum of Al/10SiC-3mica composites (Rajmohan et al. [3])

Prasad and Shobha[4]observed the microstructural characteristics of hybrid composites reinforced by SiC and rice husk ash (RHA) particles. The uniform distribution of reinforcing particles was revealed during the examination. The presence of RHA and SiC particles was also confirmed in the micrographs of hybrid composites (Figure. 3). The results of above studies indicate that it is possible to obtain nearly uniform distribution of particles in the hybrid composites. But, various parameters need to be controlled and optimized during fabrication process. However, the successful incorporation of reinforcing particles shows that it is possible to obtain the hybrid composites with isotropic set of properties.

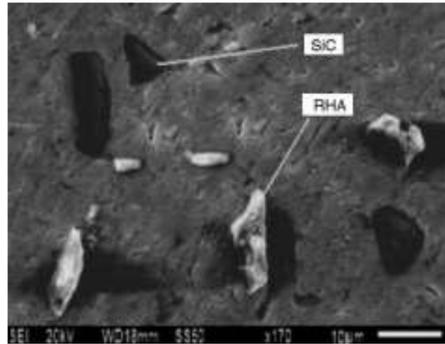


Figure3. Scanning electron micrograph of hybrid composite. (Prasad and Shobha[4])

Deravaju et al. [5] studied the influence of SiC/Gr and SiC/Al₂O₃ on the wear properties of friction stir processed Al 6061-T6 hybrid composites. The authors reported uniform distribution of the reinforcing materials in the nugget zone of the AHMMCs as shown in Figure. 4(a) and (b).

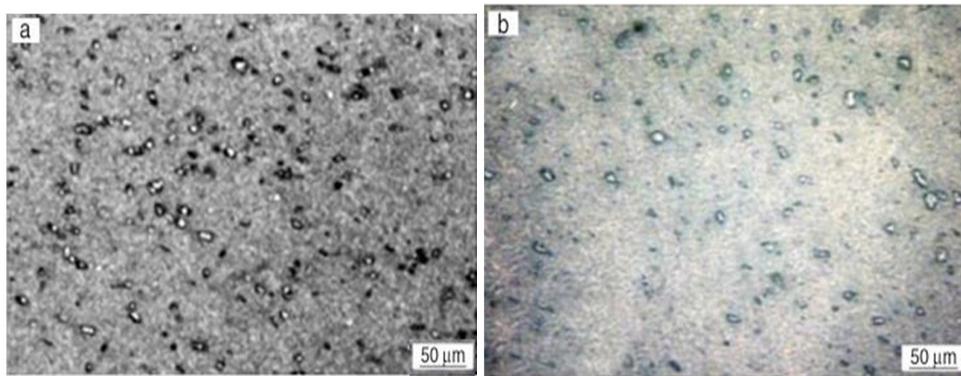


Figure4. Microstructure of surface hybrid composites (a) Al-SiC/Gr; (b) Al-SiC/Al₂O₃ (Deravaju et al. [5])

Suryakumari et.al.[11] studied Al7075 hybrid metal matrix composites (Al7075+ SiC + Al₂O₃) was produced via stir casting techniques. Al7075 is a matrix material and SiC , Al₂O₃ are the reinforcing elements. The Al7075 aluminium alloy with 2.5, 5 and 7.5 W% of SiC and 2.5, 5 and 7.5 W% of Al₂O₃ was produced via stir casting.

III. MECHANICAL PROPERTIES

The mechanical properties of a composite depend on many factors such type of reinforcement, quantity of reinforcement, shape, size etc. The proper understanding of the mechanical behaviour is thus essential as they are employed in different areas.

A. Hardness

Boopathi et al. [2] have reported an increasing trend in the hardness Figure 5(a) of composite with increase in weight fraction of reinforcements. They observed maximum hardness for Al/10 wt.%SiC/10 wt.%fly ash hybrid composites. This shows that incorporation of fly ash particles significantly improves hardness of the Al-matrix. In another study, Rajmohan et al.[3] have evaluated the hardness of the hybrid composites

reinforced with different mass fractions of mica particles (for fixed 10 wt.% SiC). The result shows that the hardness value Figure.6(a) of Al/10 wt.%SiC/6wt.%mica composite is less as compared to Al/10 wt.%SiC/3 wt.%mica composite. Low values of hardness and strength are favourable for improving machinability of composites. The results show that hardness of the AHMMCs increased more or less linearly with the fraction of mica particles. Prasad and Shoba [4] have observed that the hardness of the hybrid composites (A356.2/x%RHA/x%SiC) was higher than the pure A356.2 alloy. The hardness of the alloy increases with addition of hybrid reinforcements and the increase in hardness may be due to presence of relatively hard ceramic particles in the composite. It has also been reported that the addition of reinforcement (up to 8 wt. %) increases the hardness value by more than 50%.

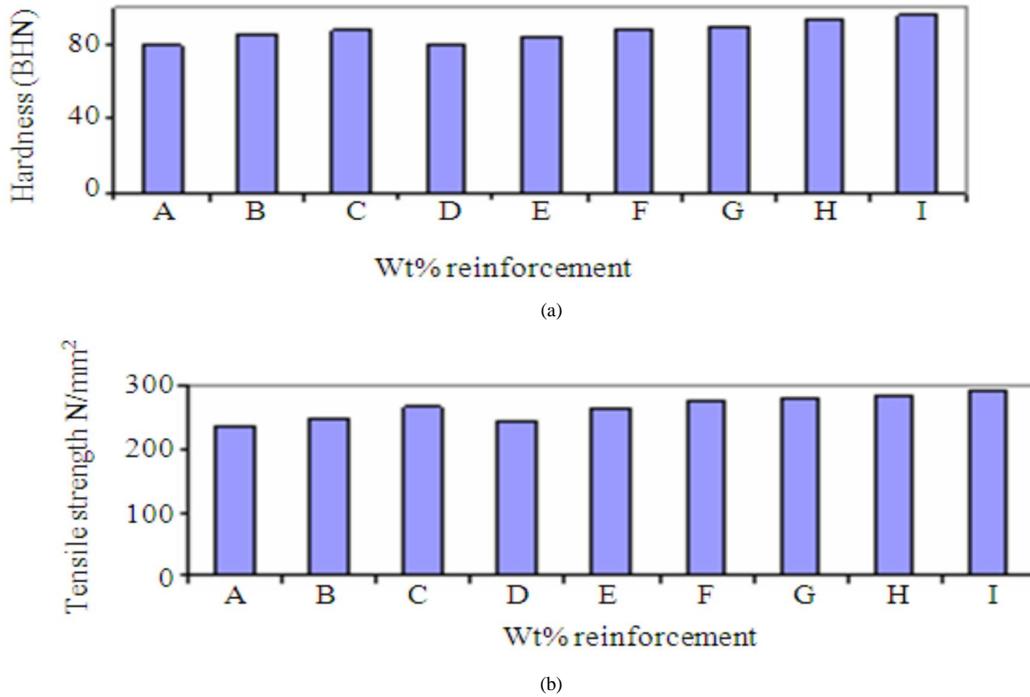


Figure 5. Graph showing variation in (a) hardness and (b) tensile strengths with different composition (A = Al, B = Al +5% SiC, C = Al +10% SiC, D = Al +5% fly ash, E = Al +10% fly ash, F = Al +5% SiC +5% fly ash, G = Al +5% SiC +10% fly ash, H = Al +10% SiC +5% fly ash, I = Al +10% SiC +10% fly ash) of hybrid MMCs (Boopathi et al. [2])

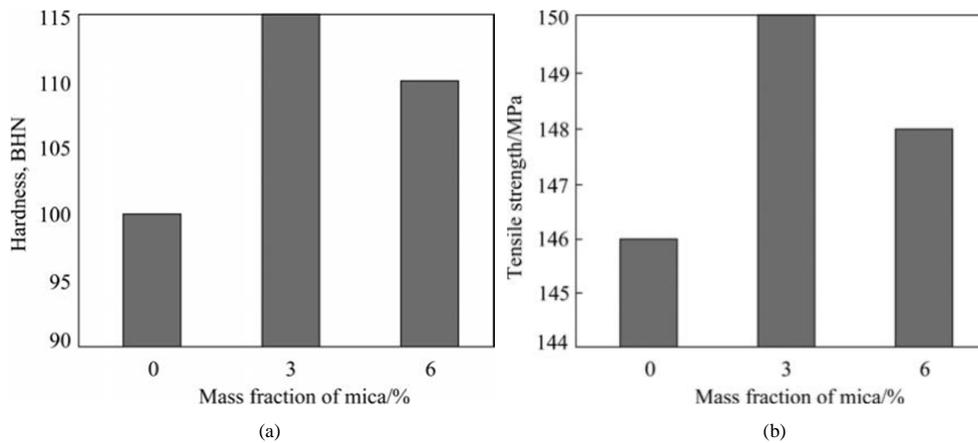


Figure 6. (a) Hardness (b) tensile strength of composite with different percentage of mica (Rajmohan et al. [3])

Suryakumari et.al [11] have performed Brinell hardness on the cast Al 7075 hybrid metal matrix composites with four trials. The effects on the hardness of Al 7075 hybrid metal matrix composites with the addition of SiC and Al₂O₃ achieved from hardness tests are shown in Figure 7. The increases in the hardness of the hybrid metal matrix composites were observed by addition of SiC and Al₂O₃ initially and the maximum hardness was achieved at 2.5% W Al₂O₃ of and 5% W of SiC. The more addition of reinforcement of SiC and Al₂O₃ leads to decreases in the hardness. Up to certain limit the addition of hard ceramic particles results in significant increase in the hardness of aluminium alloy. The hardness decreases with high weight percentage of SiC and Al₂O₃ in the hybrid metal matrix because of formation of more clustering of particles and settling down.

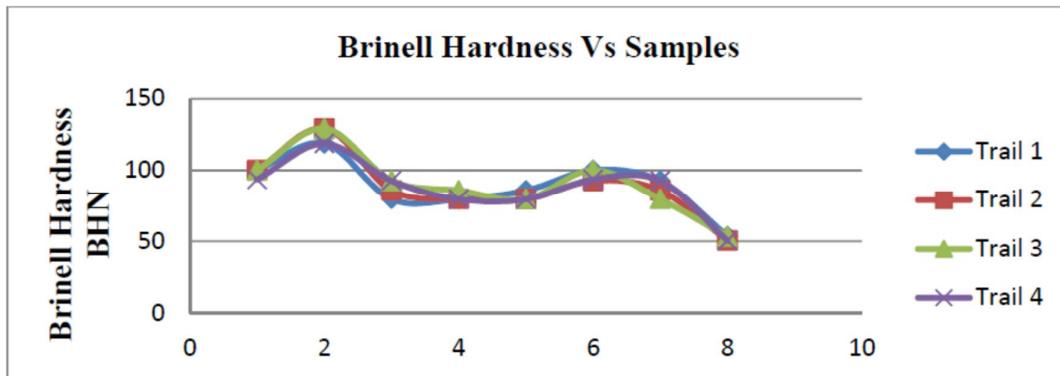


Figure 7. Brinell hardness test for Al 7075 hybrid metal matrix composites (Suryakumari et.al [11])

B. Tensile strength

Boopathi et al. Have reported the graph of the experimental tensile strength of the composites according to the SiC, fly ash and their mixtures is shown in Figure. 5(b). Results show that the tensile strength of composites is higher than that obtained for the unreinforced Al. Tensile strength of unreinforced Al is 236 N/mm² and this value increases to 265 N/mm² for Al/(10%SiC), 263 N/mm² for Al/(10%fly ash) and 293 N/mm² for Al/(10%SiC+10%fly ash) composite, which is about 57% improvement over that of the unreinforced Al matrix.

Rajmohan et al.[3] observed the tensile tests of mica reinforced composites are shown in Figure. 6.(b). The Figure indicates that the composites reinforced with 10% SiC and 3% mica particle have the highest tensile strength of 150 N/mm². At the same time, the tensile strength of composite with 10% SiC and 6% mica particle is found to be 148 N/mm². The results indicate that with the increase in mass fraction of mica, the tensile strength of the composites increases up to certain value and then reduce. In the present investigation, addition of 3% mica shows better tensile strength than the 6% mica addition.

IV. CONCLUSIONS

This paper reviews the different combination of reinforcements used in the synthesis of AHMMCs and how it influences its performance. The double synthetic ceramics reinforced AHMMCs despite showing good mechanical and tribological properties over the unreinforced alloys still need to be subjected to test under different corrosion media to ascertain its corrosion behaviour. Furthermore, comparison should be made between the hybrid composites with the single reinforced grades in order to determine how much improvement is obtained when hybrid reinforcement is used. More agro waste should be investigated and further studies should be concentrated on how to optimize the production process to determine the optimum processing parameters.

The stir casting method is found to be suitable to fabricate the aluminium hybrid metal matrix composites. Mica reinforced composites exhibits less wear loss and higher density compared with the ceramic reinforced composites. The addition of SiC and Al₂O₃ on the hardness of AHMMCs results in increases initially and decreases with more addition of weight fraction of Al₂O₃ and SiC. The high hardness value obtained with the addition of 2.5 % W of Al₂O₃ and 5% W of SiC.

REFERENCES

- [1] Michael Oluwatosin Bodunrin, Kenneth Kanayo Alaneme, Lesley Heath Chown, "Aluminium matrix hybrid composites: a review of reinforcement philosophies; mechanical, corrosion and tribological characteristics", *Journal of Materials Research and Technology*, Volume 4, Issue 4, October–December 2015, Pages 434–445.
- [2] Mahendra Boopathi, M., K.P. Arulshri and N. Iyandurai, "evaluation of mechanical properties of aluminium alloy 2024 reinforced with silicon carbide and fly ash hybrid metal matrix composites", *American Journal of Applied Sciences*, 10 (3): 219-229, 2013.
- [3] T. Rajmohan, K. Palanikumar, S. Ranganathan, "Evaluation of mechanical and wear properties of hybrid aluminium matrix composites", *Trans Nonferrous Met Soc China*, 23 (9) (2013), pp. 2509–2517
- [4] D.S. Prasad, C. Shoba, N. Ramanaiah "Investigations on mechanical properties of aluminum hybrid composites" *J Mater Res Technol*, 3 (1) (2014), pp. 79–85.
- [5] A. Devaraju, A. Kumar, B. Kotiveerachari "Influence of addition of Grp/Al₂O₃p with SiCp on wear properties of aluminum alloy 6061-T6 hybrid composites via friction stir processing" *Trans Nonferrous Met Soc China*, 23 (5) (2013), pp. 1275–1280.
- [6] K.K. Alaneme, T.M. Adewale "Influence of rice husk ash-silicon carbide weight ratios on the mechanical behaviour of Al-Mg-Si alloy matrix hybrid composites" *TribolInd*, 35 (2) (2013), pp. 163–172.
- [7] K.K. Alaneme, T.M. Adewale, P.A. Olubambi "Corrosion and wear behaviour of Al-Mg-Si alloy matrix hybrid composites reinforced with rice husk ash and silicon carbide" *J Mater Res Technol*, 3 (1) (2014), pp. 9–16
- [8] Jaswinder Singha, Amit Chauhan, "Characterization of hybrid aluminum matrix composites for advanced applications – A review", *Journal of Materials Research and Technology*, Volume 5, Issue 2, April–June 2016, Pages 159–169.
- [9] Dora Siva Prasad, Chintada Shoba, "Experimental evaluation onto the damping behavior of Al/SiC/RHA hybrid composites", *J Mater Res Technol* 2016;5:123-30.
- [10] Ravinder Kumar, Suresh Dhiman, "A study of sliding wear behaviors of Al-7075 alloy and Al-7075 hybrid composite by response surface methodology analysis", *Material and Design*, Volume 50, September 2013, Pages 351–359.
- [11] T.S.A. Suryakumari, S. Ranganathan and P. Shankar, "Study on Mechanical Properties of Al 7075 Hybrid Metal Matrix Composites", *Applied Mechanics and Materials Vols. 813-814* (2015) pp 230-234.
- [12] Jaswinder Singha, Amit Chauhan, "Characterization of hybrid aluminum matrix composites for advanced applications – A review", *Journal of Materials Research and Technology*, Volume 5, Issue 2, April–June 2016, Pages 159–169.